

# The Largest Synthetic Structure with Molecular Precision: Towards a Molecular Object\*\*

Baozhong Zhang, Roger Wepf, Karl Fischer, Manfred Schmidt, Sébastien Besse, Peter Lindner, Benjamin T. King, Reinhard Sigel, Peter Schurtenberger, Yeshayahu Talmon, Yi Ding, Martin Kröger, Avraham Halperin, and A. Dieter Schlüter\*

Since the advent of their discipline, organic chemists have sought to imitate biology through synthesis. This challenge combines four themes: chemical structure,<sup>[1]</sup> function,<sup>[2]</sup> size,<sup>[3]</sup> and molecular shape.<sup>[4]</sup> While structure and function are better understood, size and shape remain challenging. So far, chemists have not succeeded at making well-defined molecules as large as those found in biology—the highest-molecular-weight structurally precise synthetic polymer, a polystyrene, has a mass of only  $40 \times 10^6$  Da,<sup>[5]</sup> a tiny fraction of the size of the largest DNA molecules. The control of shape in large synthetic molecules is even less advanced. This feat is routine for biology—even the simplest organisms have well-

defined shapes, as exemplified by the rodlike tobacco mosaic virus (TMV). Indeed, to the chemist, the TMV is a paragon: a massive supramolecule with perfect control of chemical structure, function, size, and molecular shape. We report herein a dendronized polymer<sup>[6]</sup> that approximates the size and cylindrical shape of the TMV, thus advancing these chemical frontiers. Our synthesis relies on standard polymerization methods followed by radial expansion by using methods pioneered by Vögtle<sup>[7]</sup> and Tomalia.<sup>[8]</sup> First-generation dendrons were affixed to peripheral amino groups of the fourth-generation dendronized polymer, PG4<sub>long</sub>,<sup>[9]</sup> by using

[\*] Dr. B. Zhang, Prof. A. D. Schlüter

Department of Materials, Institute of Polymers  
 Swiss Federal Institute of Technology, ETH Zürich  
 HCI J 541, 8093 Zürich (Switzerland)  
 Fax: (+41) 44-633-1395  
 E-mail: ads@mat.ethz.ch

Dr. R. Wepf  
 EMEZ (Electron Microscopy), ETH Zurich (Switzerland)

Dr. K. Fischer, Prof. M. Schmidt  
 Institut für Physikalische Chemie, Universität Mainz (Germany)

Dr. S. Besse  
 Agroscope Changins-Wädenswil Research Station ACW, Nyon  
 (Switzerland)

Dr. P. Lindner  
 Institute Laue Langevin, Grenoble (France)

Prof. B. T. King  
 Department of Chemistry, University of Nevada, Reno (USA)

Dr. R. Sigel, Prof. P. Schurtenberger<sup>[†]</sup>  
 University of Fribourg, Adolphe Merkle Institute and Fribourg  
 Center for Nanomaterials, Marly (Switzerland)

Prof. Y. Talmon  
 Department of Chemical Engineering  
 Technion-Israel Institute of Technology, Haifa (Israel)


Dr. Y. Ding, Prof. M. Kröger  
 Department of Materials, Polymer Physics  
 ETH Zurich (Switzerland)

Prof. A. Halperin  
 Laboratoire de Spectrométrie Physique (LSP) CNRS  
 Université Joseph Fourier, Saint Martin d'Hères (France)

[†] Current address: Physical Chemistry, Department of Chemistry  
 Lund University (Sweden)

[\*\*] We thank the ETH Zürich, and the Swiss National Science  
 Foundation (NRP 62 "Smart Materials" and SCOPES IZ73Z0-  
 128169) for financial support.

Supporting information for this article is available on the WWW  
 under <http://dx.doi.org/10.1002/anie.201005164>.

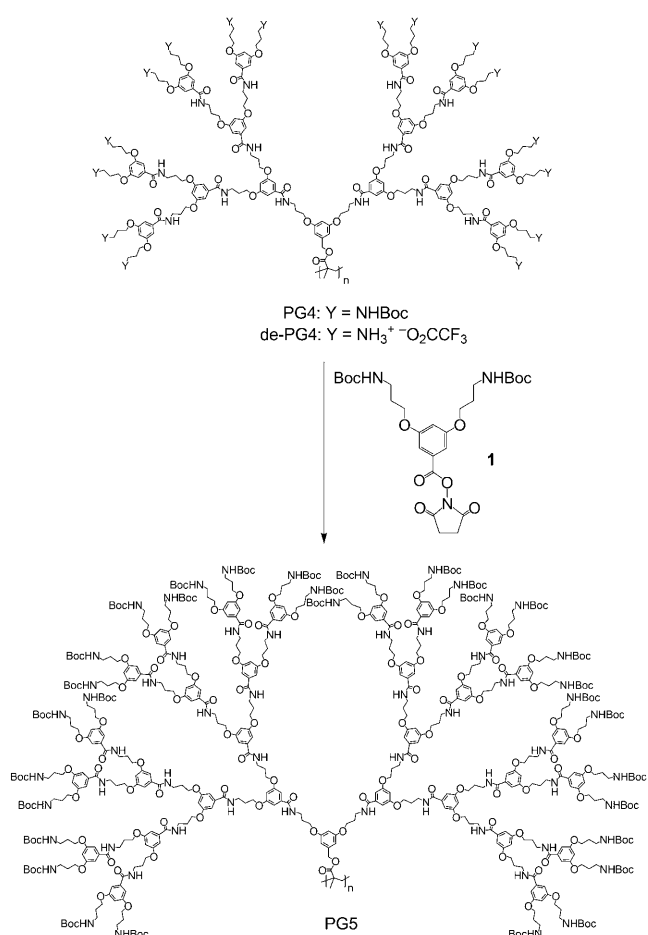

**Scheme 1.** Synthesis of PG5. Chemical structure of the first generation polymers PG4<sub>short</sub> and PG4<sub>long</sub> and their conversion to the fifth generation by deprotection and reaction with the active ester dendron 1.


Merrifield-type active ester amidation<sup>[1]</sup> to give the fifth-generation macromolecule, PG5<sub>long</sub> (Scheme 1). This synthesis requires 170 000 bond-forming reactions on a single molecule. From the known extent of conversion, the  $M_w$  of PG5<sub>long</sub> is estimated to be  $200 \times 10^6$  Da. Proving the successful accomplishment of the synthesis was challenging. The extent of conversion in the Merrifield transformation that gave PG4<sub>long</sub> was demonstrated by multi-angle laser light scattering (MALLS) molar mass determination and by UV absorption measurements of labeled samples derivatized with chromophores at unreacted sites.<sup>[10,11]</sup> The shape of PG5 was investigated on solid substrates by AFM, TEM, and scanning electron microscopy (SEM), and in solution by cryo-TEM and small-angle neutron scattering (SANS). A shorter version of the compound (PG5<sub>short</sub>) was used for the latter experiments. The shape of the macromolecules was also directly compared with TMV (Figure 1).

PG4<sub>long</sub> was obtained from PG1<sub>long</sub> through an iterative synthesis.<sup>[9]</sup> The polymer had a weight average of  $M_w = 100 \times 10^6$  Da, a corresponding degree of polymerization  $P_w = 17 600$ , a radius of gyration  $R_g = 280$  nm, and a hydrodynamic radius  $R_h = 158$  nm. The shorter analogue, PG4<sub>short</sub>, had  $M_w = 12 \times 10^6$  Da and  $M_n = 7 \times 10^6$  Da, as determined by gel permeation chromatography. The integrated structural perfection from the respective PG1 amounted to 99.4% for PG4<sub>short</sub> and to 98.5% for PG4<sub>long</sub>. MALLS and UV labeling showed that the starting material PG4<sub>long</sub> contained 170 000 peripheral amine groups (for details, see the Supporting Information).

The synthesis of PG5<sub>short</sub> and PG5<sub>long</sub> involved the removal of Boc protecting groups to give the charged de-PG4<sub>short</sub> and de-PG4<sub>long</sub> followed by an exhaustive dendronization reaction with the active ester dendron **1** (Scheme 1). AFM analysis of hundreds of single de-PG4<sub>long</sub> chains on mica did not indicate main-chain scission, as was observed for bottlebrush polymers.<sup>[6,12,13]</sup> The conversion of the dendronization reaction was 97.1% for PG5<sub>long</sub> and 97.9% for PG5<sub>short</sub>. This result leads to an average overall structural perfection of PG5 from PG1 of 94.3% (long) and 96.6% (short). From this extent of conversion and the known molecular weight of PG4<sub>long</sub>, we calculate a  $M_w$  of  $200 \times 10^6$  Da for PG5<sub>long</sub>.

The shape of PG5<sub>long</sub> was first investigated by comparison of AFM tapping mode height images of air-dried, mixed samples of PG1<sub>long</sub>–PG4<sub>long</sub><sup>[9]</sup> with PG5<sub>long</sub> on mica. Although tapping mode AFM heights ( $h_{app}$ ) depend on the experimental conditions, their comparison is meaningful if the tip–object interaction is comparable for all substrates. We find: PG1<sub>long</sub>:  $(0.4 \pm 0.1)$  nm, PG2<sub>long</sub>:  $(1.0 \pm 0.1)$  nm, PG3<sub>long</sub>:  $(2.2 \pm 0.1)$  nm, PG4<sub>long</sub>:  $(4.0 \pm 0.4)$  nm, PG5<sub>long</sub>:  $(6.2 \pm 0.3)$  nm. For PG5<sub>long</sub> on highly oriented pyrolytic graphite (HOPG)  $h_{app} = (6.5 \pm 0.3)$  nm was observed (not shown). All objects can be assigned to a particular generation (for large-scale images, see Figure S6 in the Supporting Information) and clear steps in size differentiate the generations.<sup>[14]</sup> The height increase from PG1<sub>long</sub> to PG5<sub>long</sub> is 6 nm, which suggests that PG5<sub>long</sub> does not flatten out as much as bottlebrush polymers on the mica substrate.<sup>[15,16]</sup> Next, absolute heights ( $h_{abs}$ ) were determined by TEM for air-dried PG5<sub>long</sub> on mica to give  $h_{abs} = (7.3 \pm 0.2)$  nm and absolute widths ( $w$ ) were determined by SEM for freeze-dried PG5<sub>long</sub> on amorphous carbon to give


$w = (9.4 \pm 0.3)$  nm. The  $h_{abs}$  (TEM) on mica is approximately 1 nm higher than  $h_{app}$  (AFM); this discrepancy is not unusual, as tapping mode AFM underestimates heights.<sup>[17,18]</sup> The  $h_{abs}$  and  $w$  values were compared to a simple cylinder model. The diameter of this cylinder is  $d = 9.1$  nm, assuming 1) a projected length of the backbone repeat units of 2.38 Å instead of 2.50 Å for a backbone in the all-trans conformation and 2) an estimated density of  $\rho = 1.2$  g cm<sup>-3</sup>. Thus, PG5 on mica is flattened by 1.8 nm (20%) when air-dried. Visual comparison of PG5<sub>long</sub> and the TMV by AFM is striking (Figure 1 d,e). Indeed, PG5<sub>long</sub> looks like TMV: its size, aspect ratio, and gross structure are similar. This suggests PG5 to be a molecular object, that is, a molecule the shape of which is

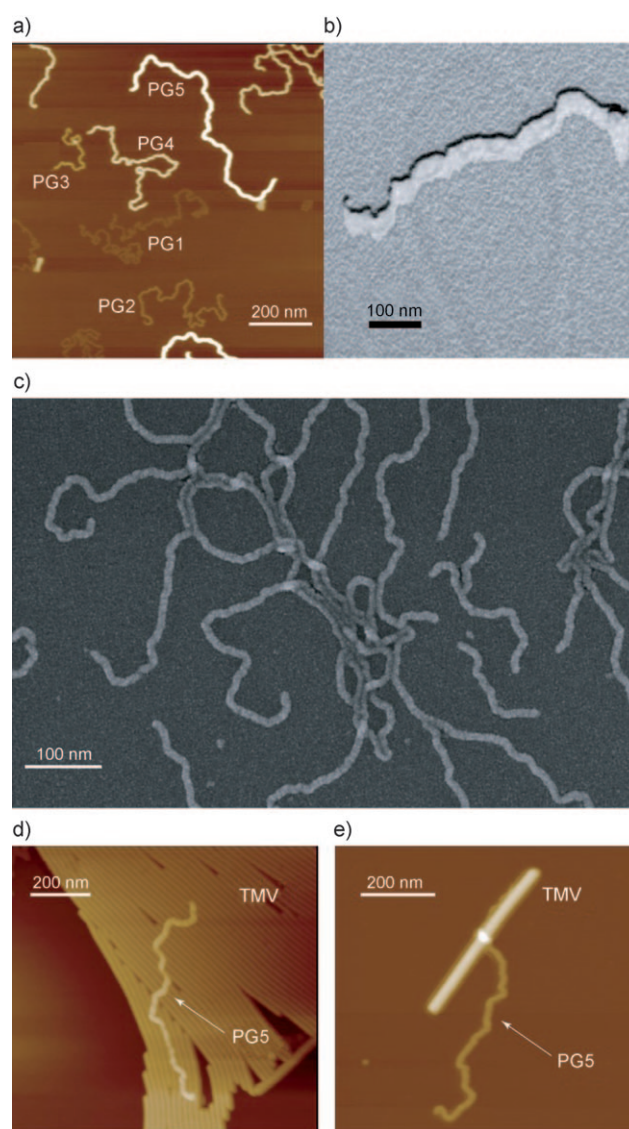

**Figure 1.** Thickness and width analysis of PG5<sub>long</sub>. a) AFM tapping mode height images of coprepared PG1<sub>long</sub>–PG5<sub>long</sub> on mica. b) TEM replica image of a unidirectional W-shadowed air-dried single chain. c) SEM image of a freeze-dried sample for width determination. d, e) AFM tapping mode height images of TMV and a single PG5<sub>long</sub> strand. The synthetic polymer is shown on an ordered monolayer array of TMV (d) and embracing a single TMV (e).

retained irrespective of its environment,<sup>[19]</sup> and to which an envelope can be assigned.

The diameter of PG5<sub>short</sub> in solution was determined by SANS and cryo-TEM. Analysis of the scattering (Figure 2a), assuming a homogeneous density and a solvated, wormlike

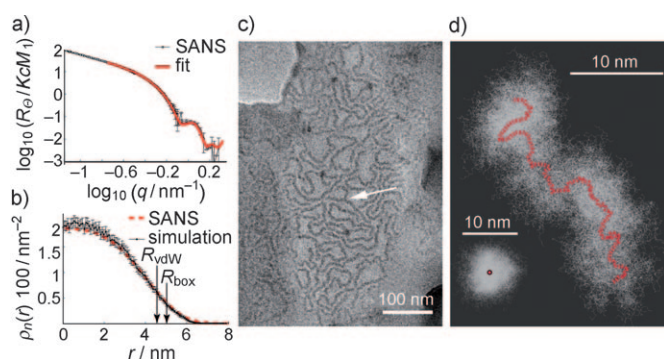

**Figure 2.** Characterization of PG5<sub>short</sub> in solution. a) SANS scattering curve in [D<sub>2</sub>]MeOH ( $K$  = contrast factor,  $c$  = concentration,  $M_1$  = monomer molecular mass). b) Density profile derived from (a) together with simulation results (see the Supporting Information for further details). c) Phase-contrast cryo-TEM image in dioxane that shows the cross-sectional diameter and the native solution conformation. The white arrow points towards a branching site. d) Snapshot of the simulated PG5 with 250 dendrons. Inset: cross-sections used to evaluate the density profile shown in (b).

polymer,<sup>[20]</sup> gave a diameter of  $d \approx 10$  nm. A more advanced cross-section analysis<sup>[21]</sup> gave the cross-section density distribution shown in Figure 2b, which is consistent with the results from the simulations also shown in Figure 2b. The diameter of PG5<sub>short</sub> in solution ( $d = 10$  nm) is similar to the width of the macromolecule when freeze-dried (SEM,  $(9.4 \pm 0.3)$  nm) and the diameter of the model cylinder ( $d = 9.1$  nm). Together with the height of the air-dried macromolecules ( $d = 7.3$  nm), it is concluded that the dimensions of PG5 both in solution and when dried on a solid substrate are comparable. We believe this to be a unique finding for synthetic polymers. This finding is qualitatively consistent with the cryo-TEM image (Figure 2c), which shows a diameter of PG5<sub>short</sub> of at least  $d = 7$  nm. Another SANS study (data not shown) confirms that chains of increasing generations are stiffer. In solution, the persistence length  $l_p$  of the thick chain (PG5<sub>short</sub>,  $l_p \approx 30$  nm) is eight times larger than that of a thin chain (PG1<sub>short</sub>,  $l_p \approx 4$  nm). Figure 2d shows a snapshot of the simulation from which the profile in Figure 2b was calculated.

PG5<sub>long</sub> is the largest covalent macromolecule with a precisely controlled structure that has ever been synthesized. This molecule is larger than amylopectin, which is amongst the largest biomacromolecules (ca.  $160 \times 10^6$  Da), and the hyperbranched polymers ( $1 \times 10^6$  Da).<sup>[22]</sup> The related “graft-on-graft” polymers reach higher molecular weights ( $500 \times 10^6$  Da),<sup>[23,24]</sup> but as in the case of the hyperbranched polymers, their chemical structure and shape are less well defined. The mass increase associated with the post-polymerization dendronization is approximately  $100 \times 10^6$  Da, which is larger than that of any polymerization leading to a structur-

ally defined product.<sup>[5]</sup> Our synthesis is short and relies on established methods. Purification is simple: the huge weight difference between product and reagents allows for filtration through silica gel and renders any Merrifield-type solid-phase procedures unnecessary.

In contrast to biology and supramolecular chemistry of nano-objects, which both create shape involving self-assembly,<sup>[25,26]</sup> we create the shape of PG5 by using covalent bonds and steric congestion. Our approach is crude but nonetheless provides macromolecules with a persistent shape that is absent from other synthetic, macromolecular architectures when adsorbed as individual entities on solid substrates.<sup>[16]</sup> PG5<sub>long</sub> is the largest synthetic molecular object<sup>[19]</sup> with a defined shape.<sup>[27,28]</sup> The surface of these dendronized polymers can be modified for various applications.

Received: August 18, 2010

Published online: December 22, 2010

**Keywords:** dendrimer synthesis · dendronized polymers · molecular objects · polymers · shape persistence

- [1] B. W. Erikson, R. B. Merrifield in *The Proteins*, Vol. 2 (Eds.: H. Neurath, R. L. Hill), 3rd ed., Academic Press, New York, **1979**, p. 259.
- [2] R. B. Woodward, *Pure Appl. Chem.* **1968**, *17*, 519–547.
- [3] H. Staudinger, *Ber. Dtsch. Chem. Ges.* **1920**, *53*, 1073–1085.
- [4] V. Percec, C.-H. Ahn, G. Ungar, D. J. P. Yearley, M. Möller, S. S. Sheiko, *Nature* **1998**, *391*, 161–164.
- [5] D. McIntyre, L. J. Fetters, E. Slagowski, *Science* **1972**, *176*, 1041–1043.
- [6] A. D. Schlüter, J. P. Rabe, *Angew. Chem.* **2000**, *112*, 860–880; *Angew. Chem. Int. Ed.* **2000**, *39*, 864–883.
- [7] E. Buhleier, W. Wehner, F. Vögtle, *Synthesis* **1978**, 155–158.
- [8] D. A. Tomalia, H. Baker, G. Kallos, S. Martin, P. Smith, *Polym. J.* **1985**, *17*, 117–132.
- [9] Y. Guo, J. van Beek, B. Zhang, M. Colussi, P. Walde, A. Zhang, M. Kröger, A. Halperin, A. D. Schlüter, *J. Am. Chem. Soc.* **2009**, *131*, 11841–11854. For some other higher-generation dendronized polymers, see: S. M. Grayson, J. M. J. Fréchet, *Macromolecules* **2001**, *34*, 6542–6544; B. Helms, J. L. Mynar, C. J. Hawker, J. M. J. Fréchet, *J. Am. Chem. Soc.* **2004**, *126*, 15020–15021; M. Yoshida, Z. M. Fresco, S. Ohnishi, J. M. J. Fréchet, *Macromolecules* **2005**, *38*, 334–344; Z.-B. Zhang, Y.-H. Teng, W. Freas, D. K. Mohanty, *Macromol. Rapid Commun.* **2006**, *27*, 626–630; S. R. Beukabbour, M. C. Parrott, S. E. A. Gratton, A. Andronov, *Macromolecules* **2007**, *40*, 5678–5688.
- [10] F. Sanger, E. O. P. Thompson, *Biochem. J.* **1949**, *45*, 563–574.
- [11] L. Shu, I. Gössl, J. P. Rabe, A. D. Schlüter, *Macromol. Chem. Phys.* **2002**, *203*, 2540–2550.
- [12] S. S. Sheiko, F. C. Sun, A. Randall, D. Shirvanyants, M. Rubinstein, H. i. Lee, K. Matyjaszewski, *Nature* **2006**, *440*, 191–194.
- [13] N. V. Lebedeva, F. C. Sun, H.-I. Lee, K. Matyjaszewski, S. S. Sheiko, *J. Am. Chem. Soc.* **2008**, *130*, 4228–4229.
- [14] C. L. Jackson, H. D. Chanzy, F. P. Booy, B. J. Drake, D. A. Tomalia, B. J. Bauer, E. J. Amis, *Macromolecules* **1998**, *31*, 6259–6265.
- [15] S. S. Sheiko, M. Möller, *Chem. Rev.* **2001**, *101*, 4099–4123.
- [16] S. Panyukov, E. B. Zhulina, S. S. Sheiko, G. C. Randall, J. Brock, M. Rubinstein, *J. Phys. Chem. B* **2009**, *113*, 3750–3768.
- [17] S. J. T. Van Noort, K. O. Van der Werf, B. G. De Groot, N. F. Van Hulst, J. Greve, *Ultramicroscopy* **1997**, *69*, 117–127.

- [18] W. Zhuang, C. Ecker, G. A. Metselaar, A. E. Rowan, R. J. M. Nolte, P. Samorí, J. P. Rabe, *Macromolecules* **2005**, *38*, 473–480.
- [19] S. I. Stupp, S. Son, L. S. Li, H. C. Lin, M. Keser, *J. Am. Chem. Soc.* **1995**, *117*, 5212–5227.
- [20] J. S. Pedersen, P. Schurtenberger, *Macromolecules* **1996**, *29*, 7602–7612.
- [21] J. S. Pedersen, P. Schurtenberger, *J. Appl. Crystallogr.* **1996**, *29*, 646–661.
- [22] B. Voit, A. Lederer, *Chem. Rev.* **2009**, *109*, 5924–5973.
- [23] M. Gauthier, M. Möller, *Macromolecules* **1991**, *24*, 4548–4553.
- [24] D. A. Tomalia, D. M. Hedstrand, M. S. Ferritto, *Macromolecules* **1991**, *24*, 1435–1438.
- [25] J. P. Hill, W. Jin, A. Kosaka, T. Fukushima, H. Ichihara, T. Shimomura, K. Ito, T. Hashizume, N. Ishii, T. Aida, *Science* **2004**, *304*, 1481–1483.
- [26] T. Shimizu, M. Masuda, H. Minamikawa, *Chem. Rev.* **2005**, *105*, 1401–1443.
- [27] For an attempt to classify nano-sized objects, see: D. A. Tomalia, *J. Nanopart. Res.* **2009**, *11*, 1251–1310; D. A. Tomalia, *Soft Matter* **2010**, *6*, 456–474.
- [28] Also see: L. Shu, A. D. Schlüter, C. Ecker, N. Severin, J. P. Rabe, *Angew. Chem.* **2001**, *113*, 4802–4805; *Angew. Chem. Int. Ed.* **2001**, *40*, 4666–4669; C. Ecker, N. Severin, L. Shu, A. D. Schlüter, J. P. Rabe, *Macromolecules* **2004**, *37*, 2484–2489. In densely packed arrays on solid substrates dendronized polymers were already claimed to be cylindrical objects: W. Stocker, B. L. Schürmann, J. P. Rabe, S. Förster, P. Lindner, I. Neubert, A. D. Schlüter, *Adv. Mater.* **1998**, *10*, 793–797.
-